

NANOTECHNOLOGY IN THE CULTURAL HERITAGE - INFLUENCE OF NANOSPENSIONS ADOPTED BY NANOPARTICLES OF TiO₂ FOR CLEANING THE SURFACE OF HISTORICAL PLASTERS

Klára Kroftová¹, Markéta Šmidtová², Ivo Kuřitka³ a David Škoda³

1. CTU in Prague, Faculty of Civil Engineering, Department of Architecture, Prague, Thákurova 7, Czech Republic; klara.kroftova@seznam.cz
2. CTU in Prague, Faculty of Civil Engineering, Department of Building Structures, Prague, Thákurova 7, Czech Republic; smidtmar@fsv.cvut.cz
3. Centre of Polymer System, Tomas Bata University in Zlin, třída Tomáše Bati 5678, Czech Republic; kuritka@utb.cz, dskoda@utb.cz

ABSTRACT

The continuous development of nanostructure and the study of physico - chemical processes in the nanometer range lead to new methods that can slow down the degradation processes of a work of art, or even restore damage caused, for example, by an inappropriate restoration process. The use of nanosuspensions based on calcium hydroxide is probably the most widespread application of nanomaterials in heritage care, especially in the field of hardening of lime building materials (plaster, limestone, etc.). In combination with titanium dioxide, it should be a successful suspension in the fight against biological agents, surface contamination or in the protection of UV-resistant building materials.

KEYWORDS

Calcium hydroxide, TiO₂, photocatalysis, nanosuspension, cleaning, antimicrobial

INTRODUCTION

Between the most common tasks encountered in the restoration of historic buildings, belongs the purification, desalting and consolidation of various types of construction materials. The biocorrosion of construction materials can be caused by bacteria, algae, lichens, plants and animals. These living organisms are able to adapt to a wide range of documents and their growth is not only affected by climatic conditions, but also by the surface moisture, chemical composition, structure and texture porosity materials.

In recent decades, nanotechnologies have become increasingly important in the area of cultural heritage care, which can facilitate the cleaning of contaminated surfaces, run self-cleaning processes and act antimicrobially, or protect the material from the negative effects of UV radiation and others. The application of nanomaterials in the care of monuments has been verified in the last approximately 15 years mainly in the form of nanosuspensions, resp. nanoemulsions based on hydroxides (especially calcium, barium, magnesium, etc.), carbonates and, in some cases, sulphates [1-3]. The advantage of the application of nanomaterials is the possibility of achieving a high penetration depth into the structure of the materials (mainly depending on the pore system and the moisture content of the material) and high efficiency while preserving the original material matter.

The use of nanomaterials is proven in practice in the deacidification of movable artworks (paper, textiles, leather [4-7]), cleaning of surfaces of historical monuments (eg. titanium hydroxide

nanosuspension, nanoemulsion of organic solvents in water etc. [8-10]) and for the consolidation of porous materials (eg. plasters, limestone or eg wall paint etc., nanodispersion of calcium hydroxide [1-3]). Successful applications of nanomaterials in crack injection or in the remediation of building materials found in humid or chemically contaminated environments and other are also documented in foreign practice [11-12].

Within the development of nanomaterials, metal oxides, especially ZnO and TiO₂, have been shown to be useful for protection against microorganisms and UV degradation due to their antifungal and antibacterial effects [13-15]. From foreign publications is known the efficiency of titanium coatings deposited on historic architectural stone surfaces as self-cleaning [16-18]. Experience in the application of oxides with different physical properties and the principles of their effects on restored materials have only recently appeared in the literature and the development of these materials is at the beginning.

The photocatalytic properties of TiO₂ were discovered by Fujisima and Honda, who first used titanium dioxide to decompose chemicals [19-20]. Titanium dioxide (TiO₂) is one of the most important and commercially available photocatalysts due to its excellent efficiency (even under low solar irradiation), low cost, compatibility with a large number of materials and good stability, where the use of photocatalytic reactions decompose the most inorganic and organic pollutants due to UV radiation. Titanium dioxide is a semiconductor material and is mainly used in anatase form. Due to its antibacterial effects, it is applied in various fields, such as water and air purification, paintings, glasses, or the cosmetics industry.

The TiO₂ nanocrystals, in the form of anatase, have a particle size in the range of several nm to 30 nm. Due to light with a shorter wavelength than 388 nm, they activate and remove oxygen atoms from some TiO₂ molecules. Next to each other coexist the hydrophilic regions depleted by oxygen and hydrophobic, unchanged (uncharged) regions. Due to the close proximity of these areas (these are areas in the order of several hundred nm²), the water droplets lose their spherical shape and form a continuous film that prevents adhesion of the pollutant to the surface [21]. This synergy of effects allows to maintain aesthetic properties, improve surface properties and slow degradation processes caused by dirt.

The photocatalytic effect of titanium dioxide produced by ultraviolet light is influenced by the size and shape of the particles and their specific surface. It is necessary to emphasize that UV radiation is absolutely necessary for the course of the reaction and that TiO₂ has a catalyst function and therefore does not decrease. However, to maintain long-lasting high efficiency, it is necessary to maintain surfaces (treated with TiO₂) and remove reaction products (eg. by water or rain).

The TiO₂ nanoparticles themselves are chemically inert, very stable over time and, according to their current knowledge, non-toxic to humans. The presence of metal oxides such as WO₃, ZrO₂, MoO₂, or also CdS and the doping of TiO₂ by nitrogen can significantly affect the course of photocatalysis [22]. However, the problem of dispersed TiO₂ nanoparticles in the nanocoating is the tendency to form clumps after a certain period of time in the liquid environment. This leads to enlargement of the average particle size of TiO₂ and the photocatalytic potential decreases.

MATERIALS AND METHODS

The goal of laboratory research was to create a multifunctional nanoparticle and titanium dioxide based compound that would give very good results to historic surfaces (especially plaster and stone) in the mean of self-cleaning surface and simultaneously to add the missing binder. Applying nanomaterial would not change the original appearance, as a result of the photocatalytic phenomenon would reduce the rate of deposition of pollutants and thus slow the development of degradation processes. TiO₂ nanoparticle suspension allows thin transparent coatings on the surface of the treated material to act as a preventive protective system activated by solar UV radiation while reducing existing pollution and retarding degradation processes.

--

The incorporation of TiO_2 into nanosuspension of calcium hydroxide was carried out within the framework of the NAKI research project in cooperation with the TBU Polymer Systems Center in Zlín.

For the preparation of nanosuspensions were used the following chemicals: Calcium methoxide ($\text{Ca}(\text{OCH}_3)_2$, 97 %, $M_w = 102,15 \text{ g mol}^{-1}$), Titanium(IV) isopropoxide ($\text{Ti}(\text{OC}_3\text{H}_7)_4$, 97 %, $M_w = 284,22 \text{ g mol}^{-1}$) and isopropyl alcohol (p.a.) were purchased by Sigma-Aldrich.

The nanosuspension of $\text{Ca}(\text{OH})_2$ (Ca1) was produced by hydrolysis of calcium methoxide $\text{Ca}(\text{OCH}_3)_2$ (average particle size according to DLS 298 nm, Figure 1, Table 1, [23]). The nanosuspension sample CaTi1 was prepared by hydrolysis of $\text{Ca}(\text{OCH}_3)_2$ and $\text{Ti}(\text{OC}_3\text{H}_7)_4$ mixture in isopropyl alcohol/water solvent. The reaction mixture was stirred at room temperature, the obtained suspension was separated by centrifugation and washed with water and isopropyl alcohol. The final product was dried in the oven at $80 \text{ }^\circ\text{C}$ for 1 hour. Yield = 4,21 g (81 %), (theoretical yield 5,20 g). See the Table 1 for more details.

The nanolime suspension was prepared by dissolving 0.75 g of the product in 250 ml of isopropyl alcohol. To increase the homogeneity of the resulting dispersion, the suspension was placed in an ultrasonic bath for 1 hour.

Table 1 - Precursor amounts and product yields

sample	precursor	m precursor (g)	n precursor (mmol)	yields (g)
Ca1	$\text{Ca}(\text{OCH}_3)_2$	7,18	70,2	4,21
CaTi1	$\text{Ca}(\text{OCH}_3)_2$	5,79	56,6	4,95
	$\text{Ti}(\text{OC}_3\text{H}_7)_4$	5,61	19,7	

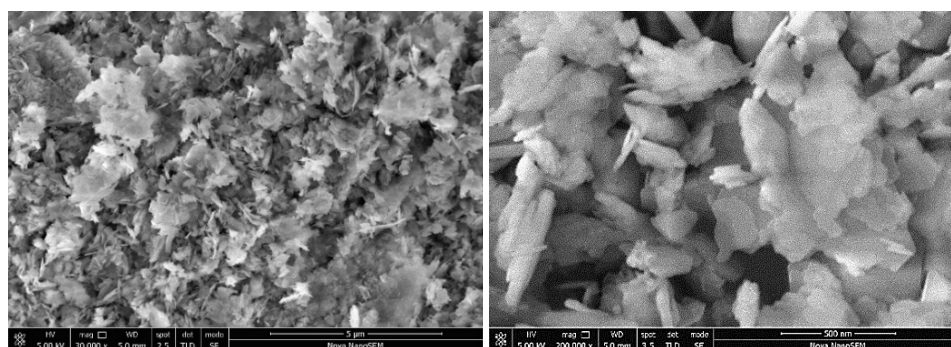


Fig. 1 - SEM images of the test product of nanosuspension Ca1 without dopant TiO_2 . There are well visible hexagonal, very thin (approx. 50 nm) platelet crystals on the images (Nova NanoSEM (FEI) with Schotky field emission electron source (0.02–30 keV) and TLD detector, Photo CPS UTB Zlín)

For the identification of crystalline phases and confirmation of presence of $\text{Ca}(\text{OH})_2$ in prepared products powder XRD diffraction analysis was employed. Powder XRD patterns were recorded on Rigaku MiniFlex 600 equipped with a CoK_α ($\lambda = 1.7903 \text{ \AA}$) X-ray tube (40 kV, 15 mA). Diffraction patterns are displayed in Figure 2. All diffractions are assigned to $\text{Ca}(\text{OH})_2$ phase and they correspond to the JCPDS database card number 076-0571. In the case of sample CaTi1 with the titanium, no diffractions related to TiO_2 were detected. The absence of TiO_2 diffractions means

that titanium species are presented in the amorphous form. This amorphous form is characterized most probably by oligomeric titanium oxo clusters with tetracoordinated and hexacoordinated titanium atoms.

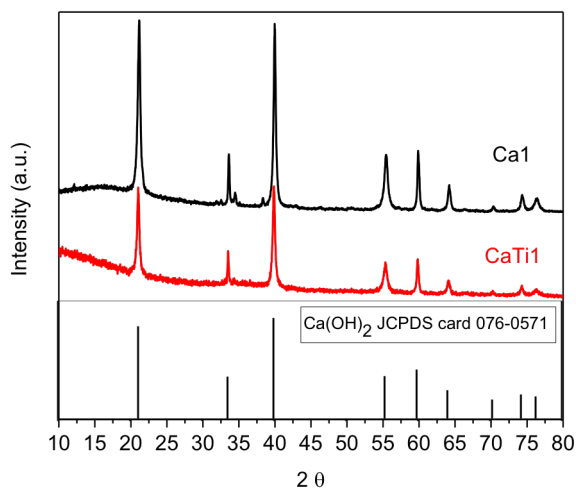


Fig. 2 - The XRD diffractogram of the tested nanosuspension of Ca1 and CaTi1 and their comparison with the $\text{Ca}(\text{OH})_2$ library diffractogram

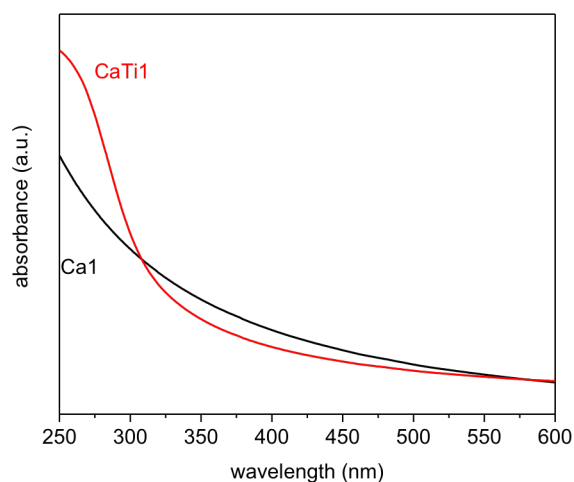


Fig. 3 - UV-Vis spectra of nanosuspensions Ca1 and CaTi1.

The important factor of $\text{Ca}(\text{OH})_2$ nanosuspensions is the size of nanoparticles. The nanoparticle sizes were measured by dynamic light scattering method. DLS size distribution measurements were performed on the Zetasizer Nano ZS from Malvern. Obtained results are illustrated in Table 2. For the comparison of nanoparticle size, commercially available nanosuspension CaLoSiL® was used within this measurement as well. Based on the obtained values we can conclude, that both $\text{Ca}(\text{OH})_2$ and $\text{Ca}(\text{OH})_2/\text{TiO}_2$ nanodispersions prepared via hydrolysis of the alkoxides provides the systems with the nanoparticle size close to commercial CaLoSiL®.

Table 2 - Particle size measurements by DLS method.

sample	average		
	Z-Ave (nm)	Peak1 (nm)	PDI
Ca1	298	275	0,269
CaTi1	249	241	0,231
CaLoSiL®	146	176	0,172

UV-Vis spectroscopy is important characterization technique for titanium species. Titanium dioxide exhibits absorption in UV region. This property is also crucial for the photocatalytic efficiency. With the application of UV-vis spectroscopy we can determine presence of Ti species represented by oligomeric titanium oxo clusters with tetracoordinated and hexacoordinated titanium atoms in mixed $\text{Ca}(\text{OH})_2/\text{TiO}_2$ nanosuspensions. UV-Vis spectra measurements were performed on Perkin-Elmer Lambda 1050 with the Xe lamp and are displayed in Figure 3. Significant difference between $\text{Ca}(\text{OH})_2$ (Ca1) and mixed $\text{Ca}(\text{OH})_2/\text{TiO}_2$ (CaTi1) nanosuspension is observed in UV region where absorption of Ti species takes place. This absorption is represented by the steep increase of absorbance at ca. 330 nm.

CONCLUSION

From the results obtained, it is obvious that the use of prepared lime nanosuspension with TiO_2 dopant as a protective and self-cleaning layer of building materials exposed to weathering and UV radiation is promising. The present preparation of $\text{Ca}(\text{OH})_2$ and $\text{Ca}(\text{OH})_2/\text{TiO}_2$ nanosuspension by the hydrolysis of alkoxides yields results that are close to the commercial CaLoSiL^\circledR material. The advantage of the hydrolytic method is the purity of the resulting product and the relatively small particle size. The addition of titanium isopropoxide to the reaction mixture makes it possible to obtain $\text{Ca}(\text{OH})_2$ nanoparticles with Ti species that will function as photocatalytically active centers. In our case, Ti species are amorphous in form of oligomeric titanium oxo clusters.

The issue of the preparation and application of a multifunctional suspension is still subject of laboratory testing. Identifying suitable manufacturing processes could lead to the practical use of nanosuspension in building and conservation practice.

ACKNOWLEDGEMENTS

The results of the research carried out under this contribution have been achieved with the financial support of the NAKI II project DG16P02M005 "*Development and research of materials, processes and technologies for the restoration, preservation and consolidation of historical brick structures and surfaces and systems for the preventive protection of historical and listed buildings endangered by anthropogenic and natural hazards* (2016 - 2011, MK0 / DG)".

REFERENCES

- [1] Macháčko, L. et al, 2012. Testování „nanosuspenzí“ na bázi hydroxidu vápenatého v rámci projektu Stonecore, In. Sborník semináře Nanomateriály v památkové péči, STOP, str. 32 – 36
- [2] Rathouský, J., 2012. Nanovápno pro konsolidaci porézních materiálů – principy, mechanismy, In. Sborník semináře Nanomateriály v památkové péči, STOP, str. 28 – 31
- [3] Škrdlantová, M. et al. 2012. Laboratorní použití micelárních roztoků a mikroemulzí při čištění historických materiálů. In. Sborník semináře Nanomateriály v památkové péči, STOP, str. 18 – 22
- [4] Baglioni, P. et al. 2012. Nano-Materials for the Conservation and Preservation of Movable and Immoveable Artworks, Progress in Cultural Heritage Preservation – EUROMED 2012, dostupné online: https://www.researchgate.net/publication/270365605_Nano-Materials_for_the_Conservation_and_Preservation_of_Movable_and_Immoveable_Artworks
- [5] Poggi, G. et al. 2010. Hydroxide Nanoparticles for Deacidification and Concomitant Inhibition of Iron-Gall Ink Corrosion of Paper, Langmuir, 26 (24), pp 19084–19090
- [6] Kwitkowska, A. et al. 2014. A.Paper deacidification with the use of magnesium oxide nanoparticles, Forestry and Wood Technology № 85, p.144-148, dostupné online: http://agro.icm.edu.pl/agro/element/bwmeta1.element.agro-4b9d7961-05a7-43ed-9339-708f4ba9365a/c/144_Annals85.pdf
- [7] Giorgi, R. et al. 2002. Nanotechnologies for Conservation of Cultural Heritage: Paper and Canvas Deacidification, Langmuir, 18 (21), pp 8198–8203
- [8] Graziani, L. et al, 2014. Durability of self-cleaning TiO_2 coatings on fired clay brick facades: Effect of UV exposure and wet & dry cycles, Building and Environment, 2014, Vol.71, p.193-203 Dostupný online: <http://www.sciencedirect.com/science/article/pii/S0360132313002904>.
- [9] Quagliarini, E. et al. 2012. Smart surfaces for architectural heritage: Preliminary results about the application of TiO_2 based coating on travertine, Journal of Cultural Heritage, Vol.13, p.204-209
- [10] Quagliarini, E. et al. 2013. Self-cleaning materials on Architectural Heritage: Kompatibility of photo-induced hydrophobicity of TiO_2 coatingy on stone surfaces, Journal of Cultural Heritage, Vol.14, p.1-7
- [11] Gavenda, M. et al. 2005. Consolidación y restauración de revocos esgrafiados en la iglesia parroquial de Nuestra Señora de la Asunción de Traiguera, Loggia Restoration, Año VIII, No.18, p.64-69

--

- [12] Liu, T. et al. 2010. Structure stability and corrosion resistance of nano-TiO₂ coatings on aluminum in seawater by a vacuum dip-coating method, *Surface and Coatings Technology*, Volume 205, Issue 7, p. 2335–2339
- [13] De Filpo, G. et al. 2013. Preventing fungal growth in wood by titanium dioxide nanoparticles, *INTERNATIONAL BIODETERIORATION & BIODEGRADATION*, vol. 85 pp. 217–222
- [14] Pinho, L. et al. 2013. A novel TiO₂–SiO₂ nanocomposite converts a very friable stone into a self-cleaning building material. *Applied Surface Science* [online]. Vol. 275, s. 389-396 [cit. 2013-11-14]. DOI: 10.1016/j.apsusc.2012.10.142. ISSN 0169-4332. Dostupný online: <http://www.sciencedirect.com/science/article/pii/S0169433212018831>.
- [15] Gomez-Ortiz, N. et al. 2013. Antifungal Coatings Based on Ca(OH)₂ Mixed with ZnO/TiO₂ Nanomaterials for Protection of Limestone Monuments, *ACS APPLIED MATERIALS & INTERFACES* Vol. 5 Iss. 5 Pp. 1556-1565
- [16] Revuru, A. N. et al.: Photo Catalytic Activity of Anatase TiO₂/PVA Film Coated Plate. In: *Advanced Materials Research*, 584, 396 (2012).
- [17] Allen, G. C. et al. 2002. Photocatalytic oxidation of NO_x gases using TiO₂: a surface spectroscopic approach. In: *Environmental Pollution* 120, pp. 415–422.
- [18] Wang, H. et al. 2013. Multifunctional nanocomposites for paper conservation, *STUDIES IN CONSERVATION* Volume: 58 Issue: 1 Pages: 23-29
- [19] Fujishima, A. 2005. Discovery and applications of photocatalysis – Creating a comfortable future by making use of light energy. In: *Japan Nanonet Bulletin*, 44th Issue
- [20] Hashimoto, K. et al. A. TiO₂ Photocatalysis: A Historical Overview and Future Prospects, *Japanese journal of applied physics*, vol. 44, No. 12, p. 8269 – 8285, dostupné online: https://www.jsap.or.jp/jsapi/Pdf/Number14/04_JJAP-IRP.pdf
- [21] Bílý, P. et al. Experimentální studie vlivu nanomateriálů na fotokatalytické vlastnosti betonu, dostupné online: <http://stavba.tzb-info.cz/beton-malty-omitky/14178-experimentalni-studie-vlivu-nanomaterialu-na-fotokatalyticke-vlastnosti-betonu>
- [22] Hochmannová, L. et al. 2010. Vliv nanočástic TiO₂ a ZnO na fotokatalytické a mikrobiální činky silikátových nátěrů, *Chem. Listy* 104, 940-944
- [23] Kroftová K., et al. 2017. Synthesis nanolime suspensions and their potential use in cultural heritage preservation, konference EASEC-15, October 11-13, Xi'an, China